

# Influence of chemical treatment in synthesize and characterization sisal/glass hybrid composite

Cite as: AIP Conference Proceedings **2283**, 020065 (2020); <https://doi.org/10.1063/5.0024883>  
Published Online: 29 October 2020

Sanjeevi Basker, A. Parthiban, R. Saravanan, V. Vijayan, T. Sathish, and I. J. Isaac Premkumar



View Online



Export Citation

Meet the Next Generation  
of Quantum Analyzers

And Join the Launch  
Event on November 17th



Register now



Zurich  
Instruments



# Influence of Chemical Treatment in Synthesize and Characterization Sisal/Glass Hybrid Composite

Sanjeevi Basker<sup>1, a)</sup>, A. Parthiban<sup>1, b)</sup>, R. Saravanan<sup>2, c)</sup>, V. Vijayan<sup>3, d)</sup>, T. Sathish<sup>4, e)</sup>  
and I.J. Isaac Premkumar<sup>5, f)</sup>

<sup>1</sup>*Dept. of Auto. Engg., VELS Institute of Sci., Tech. & Advanced studies, Chennai, TN, India.*

<sup>2</sup>*Ellenki College of Engg. and Tech., Hyderabad, TS, India.*

<sup>3</sup>*Dept. of Mech. Engg., K.Ramakrishnan College of Technology, Trichy TN, India.*

<sup>4</sup>*Dept. of Mech. Engg., Saveetha School of Engineering, SIMATS., Chennai, TN, India*

<sup>5</sup>*Dept. of Mech. Engg., JCT College of Engg. and Tech., Coimbatore, TN, India.*

<sup>a)</sup>Corresponding author: baskar133.se@velsuniv.ac.in

<sup>b)</sup>parthibana@yahoo.co.in

<sup>c)</sup>dr.sarravanan@gmail.com

<sup>d)</sup>vijayan.me@gmail.com

<sup>e)</sup>sathish.sailer@gmail.com

<sup>f)</sup>isaacpremkumar007@gmail.com

**Abstract.**Materials are indispensable but the supply is limited. In particular, the supply of material is limited for specific applications. Light weight low strength applications are very wide. This investigation focuses the natural fibre hybrid with artificial fiber based hybrid composite preparation. The sisal fibre is used to prepare the composite with glass fibre. The sisal fiber is here treated with specific concentration of sodium oxidanide in the distilled water. The composites synthesized with treated and untreated sisal fibres. The alternate fashion of horizontal and vertical is followed for fibres' orientation. The bio epoxy is employed as matrix material with mix of hardener. The prepared composite are characterized by water absorbability, tensile properties, flexural properties and shock absorption capacities. The synthesized composites also characterized for dry and wet applications.

## INTRODUCTION

Material consumptions are increased day by day drastically. The supply of material on conventional basis like metal is highly insufficient to meet those requirements. On another side the demand for materials which possess the high strength and low weight is preferred more than conventional material. So the researchers invent new materials to meet such demand. [1] Used almond shell powder and mix with resin to prepare the particulate composite panels by compression molding process. Similarly [2] suggested such composite fabrication with use of powder of skin removed tamarind seeds for fabricating the panels for commercial use. [3] Suggested the treated Sisal fibers will improve the mechanical properties. So they experimented and [3] suggested suitability of material by use of Sisal fibers treated with NaOH solution and selected jute fiber for hybrid composite laterally they suggested Sisal fiber treated by mallic acid with glass fiber for another kind of composite material [4]. [5] Suggested a methodology for Z-axis reinforcement that is prevention of de-lamination by stitching before compression for removing the excess resin and air gaps and for ensuring predefined uniform thickness. This research focuses to examine the NaOH and KmnO4 treated Sisal fiber and the artificial glass fiber with specific number of layers and pre defined best bonding orientation of fibers to obtain the composite material for both dry and wet applications. .

## MATERIALS AND METHODS

### Composite Matrix

The matrix materials are mainly consists of selectively obtained and specially prepared high quality sisal fiber (Figure 1a), the commercially available high quality glass fiber (Figure 1b) for reinforcement. The low cost, best match for sisal fibre based composite's bonding agents, the cashew nut cell oil is employed as resin and also bought the suitable hardener for the same [6-22]. The poly vinyl acetate is employed as releasing agent[23-35]. The high quality sisal fiber was prepared from the naturally harvested sisal leaves by decortications, followed by drying further the fibre qualities were enhanced by chemical treatment[36-47].

TABLE 1. Desirable properties of Preferred Fibres

Name of the Fibre	Tensile Strength (MPa)	Density (kg/m <sup>3</sup> )	Young's Modulus (MPa)	Flexural Modulus (MPa)
Sisal Fibre	68	1450	3774	125000 - 17500
Glass Fibre	2500-3500	2.5	70000	70000 - 73000



(a)



(b)

FIGURE 1. (a) Treated SisalFibre (b) Branded Glass Fibre

### Refining Quality of Sisal and Sisal Fiber

The low cost and appreciable enhancement was achieved through sodium oxidanide treatment [3,48-61]. Here it was preferred that volume fraction of 0.5% of sodium oxidanideand 0.5% and Potassium Permanganate with distilled water. The high quality sisal fibers soaked in the solution for 240 minutes followed by drying on open space with normal sunrays (do not being at hot sunrays) for 120 minutes that is dried in the morning 8AM to 10 AM. After that the fibres cut to 5 cm long[62-70].

### Synthesis of Hybrid Composite

The preferred selective sequence of layers and orientation of fibers on each layer are alternate fashion of horizontal and vertical. A chromium- plated MS, Square shaped molds (of side 30 cm) are placed n the molding table. The parting (Wax) agent applied on the mould which will facilitate release the finished. The planned layer details are

furnished in the Table 2. Beadings at the corners of models are maintained the preplanned gap. The preplanned length of 50 mm followed for both sisal fibre and glass fibres. The glass fibers used for extreme layers that top and bottom. In between layers sisal but their fashions are alternate orientation of fibres in horizontal and vertical directions. The layers are bonded with just prepared paste of mix of 10 part of resin and one part of hardener. Finally entire composite panel was compressed in CTM and kept in the compressed position for 3 to 4 hours, by which the voids filled up, air bubbles removed and excess resin content also removed. Then panels allow drying in sun light with weight for avoiding bending due to shrinkage while drying. Hence the composite samples are prepared by the combination of compression moulding and manual layup technique.

## CHARACTERIZATION

### Investigation on Water Absorbability

According to ASTM D570, the prepared samples are preheated in the air over in the rage of 45 to 55 degree centigrade temperature settings. The composites samples are kept immersed in distilled water at room temperature around 25 to 35 degree centigrade of temperature. At every day and weighed after wiped out the water content on the surface of panels. On the first day the weight gain with the resolution of 0.01 mg is more and comparative decreases of weight gain day by day. Hence it was noted that the proposed hybrid composite absorbs the moisture. I was also found that the inflammation in tested hybrid composite samples. It was planned that better the proposed composite characterized in terms of its strength / property under wet condition than in term of water absorbability. So certain panels were allow immersing in water up to five days and used them to characterize its properties under wet condition.

**TABLE 2.** Water Absorbability of Treated and Untreated Sisal Fibre based Hybrid Composite

Characterization Criteria	Composite Specimen	
	Treated	Untreated
Net Water Absorbed in grams	5.00	7.82

### Characterization under Co-linear unlike Loads

**TABLE 3:** Characterization of Treated and Untreated, Dry and WetHybridComposite under Co-linear unlike load

Characterization Criteria	Dry Specimen		Wet Specimen	
	Treated	Untreated	Treated	Untreated
	Tensile strength in MPa	57.38	47.46	57.89
Tensile Modulus in Mpa	297.24	240.02	292.41	246.32



**FIGURE 2.** Sample Specimen of Hybrid Composite for Characterizing Properties under Co-linear unlike load

In the Co-linear type unlike loading investigation is for characterizing the material in terms of properties by tensile load by use of the specimen prepared to the standard of ASTM D3039 that is rectangular of size 1x10 sq. inches (Figure 2). The maker of FIE universal testing machine UTE-40 type 400 KN capacity was employed for this investigation. The loading speed is 1 mm per minute was set. As per standard the 150 millimeter of gauge length was set. The environment conditions are an average relative humidity of 50% and the temperature about 35°C. The observations obtained for both dry and wet composite and presented them in the Table 3.

### Characterization under Transverse or Orthogonal Load

In the Transverse or Orthogonal loading is used for characterizing by Flexural strength on is for the material in terms of properties by three point bending method. The specimen prepared to the standard of ASTM D790 that is 3 mm thick rectangular of size 157x 13sq. millimetres (Figure 2). The same FIE universal testing machine UTE-40 type 400 KN capacity was employed for this investigation. The loading speed is 1 mm per minute was set. As per standard the 150 millimeter of gauge length was set. The environment conditions are an average relative humidity of 50% and the temperature about 35°C. The observations obtained for both dry and wet composite and presented them in the Table 4.

**TABLE 4:** Characterization of Dry and Wet(G-S-S-S-G) Hybrid Composite under Orthogonal load

Characterization Criteria	Dry Specimen		Wet Specimen	
	Treated	Untreated	Treated	Untreated
Flexural strength in MPa	13.86	9.64	14.28	11.24
Flexural Modulus in MPa	1586	1123	1602	1142



**FIGURE 3.** Sample Specimen of Hybrid Composite for Characterizing Properties under Orthogonal load

## Characterization Hybrid Composite for Toughness

The Toughness of the materials is usually characterized by Impact Test Method. Charpy Test setup is employed in this investigation. The specimen prepared under the standard of ASTM D256 to the dimensions of 2½ x ½ x 1/8 Cubic Inches. The energy observed by the specimen is observed. And tabulate in Table 5. The specimen is shown in figure 4. The investigation ambient conditions are room temperature and 50% the average RH

**TABLE 5:** Characterization of Dry and WetHybrid Composite under Impact load

Characterization Criteria	Dry Specimen		Wet Specimen	
	Treated	Untreated	Treated	Untreated
Observed Energy in joules	16.48	10.82	16.78	11.36




**FIGURE 3.** Sample Specimen of Hybrid Composite for Characterizing Properties under Impact load

## RESULTS AND DISCUSSIONS

### Water Absorbability


The water absorbability was investigated in treated sisal fibre and untreated sisal fibre based specimens. It was found that the treated sisal fibre based specimen absorbed less water than untreated sisal fibre based composite specimens (Refer Figure 4).

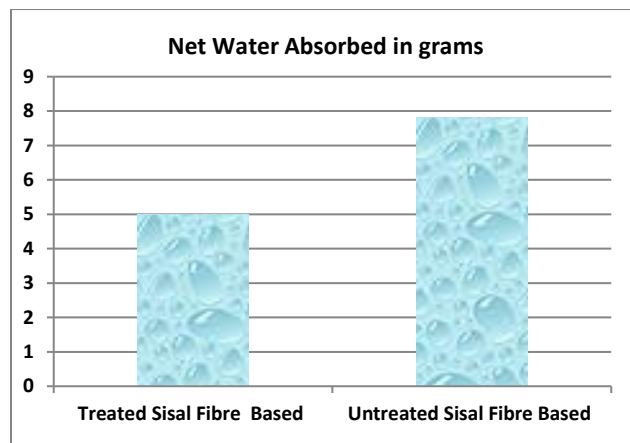


**FIGURE 4.** Water absorbability of Hybrid Composites

## Tensile properties

The tensile properties like tensile strength and tensile modulus of the treated Sisal fibre based hybrid composites got improved (Refer Figure 5 and Figure 6). The wet composite is stronger in tension than dry specimen (Refer Figure 5 and Figure 6).

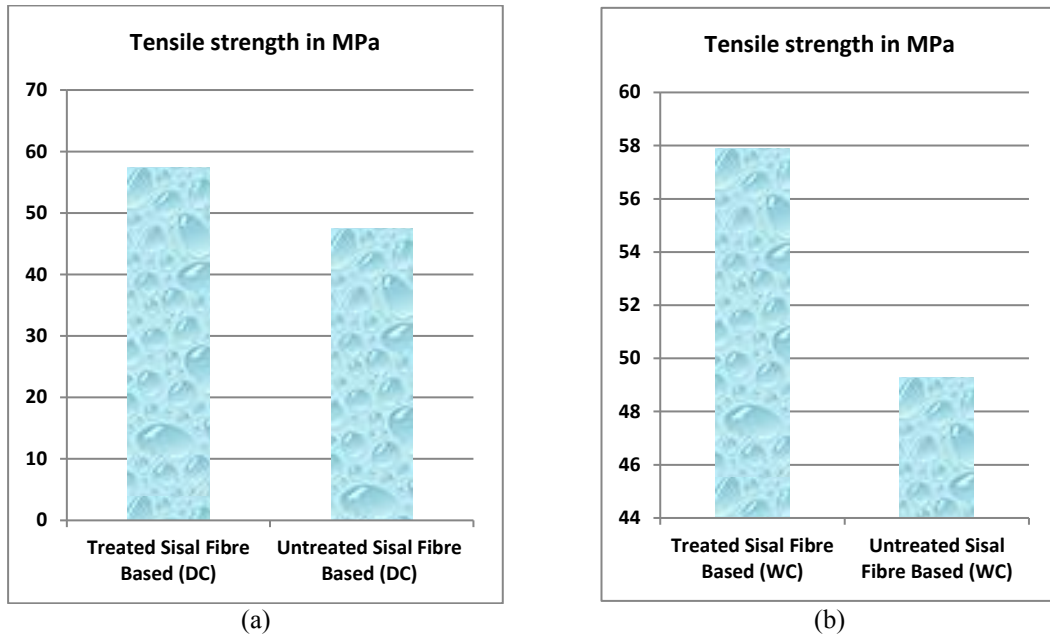


**FIGURE 5.** Tensile Strength of Treated and Untreated Sisal fibre based (a) Dry Composite (DC) (b) Wet Composite (WC)

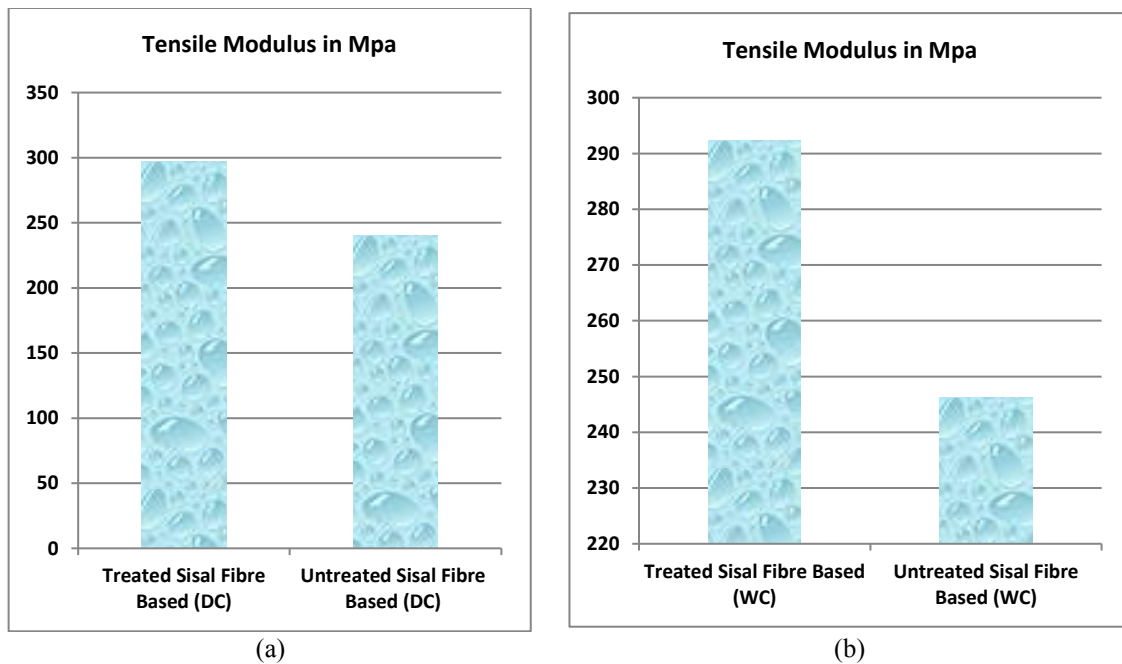


**FIGURE 6.** Tensile Modulus of Treated and Untreated Sisal fibre based (a) Dry Composite (DC) (b) Wet Composite (WC)

## Flexural Properties

The Flexural Properties like flexural strength and flexural modulus of the treated Sisal fibre based hybrid composites got improved (Refer Figure 7 and Figure 8). The wet composite is stronger in bending than dry treated Sisal fibre based hybrid composite (Refer Figure 7 and Figure 8).

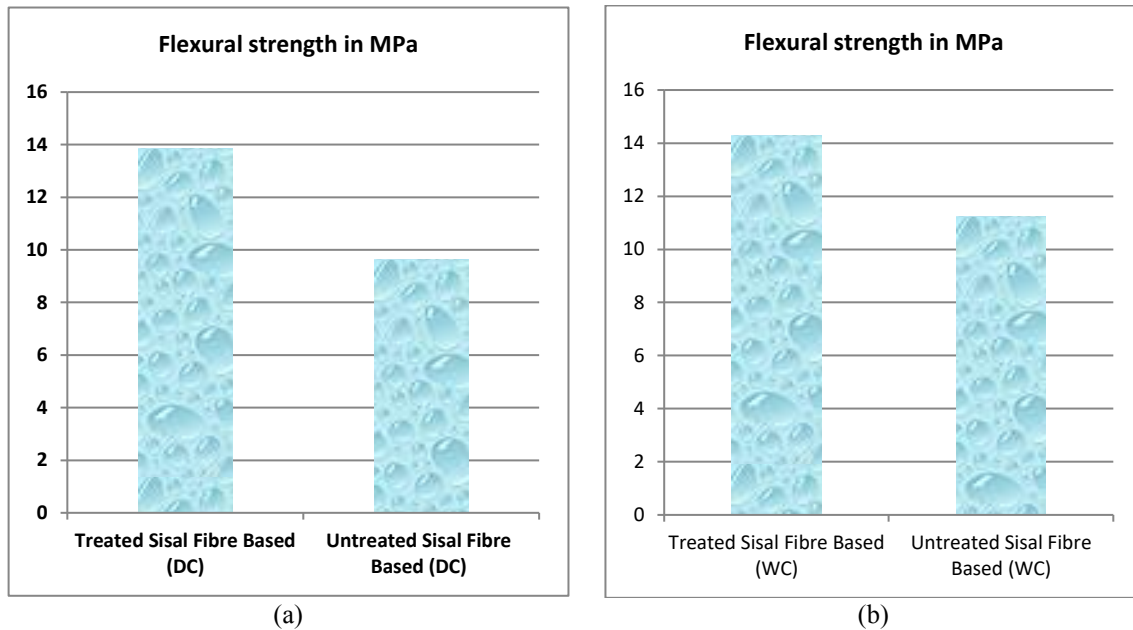

**FIGURE 7.** Flexural Strength of Treated and Untreated Sisal fibre based (a) Dry Composite (DC) (b) Wet Composite (WC)

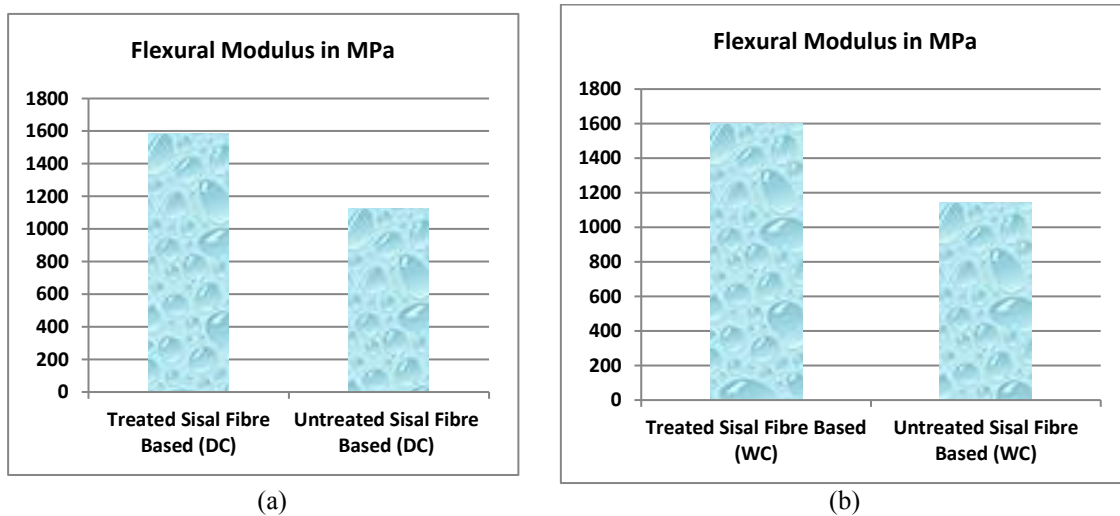

**FIGURE 8.** Flexural Modulus of Treated and Untreated Sisal fibre based (a) Dry Composite (DC) (b) Wet Composite (WC)



## Shock Absorbability

The impact load or shock load based test namely charpy is employed for this investigation. The results reveal that impact strength of the treated Sisal fibre based hybrid composites got improved (Refer Figure 9). The wet treated Sisal fibre based hybrid composite is stronger in bending than dry treated Sisal fibre based hybrid composite (Refer Figure 9).

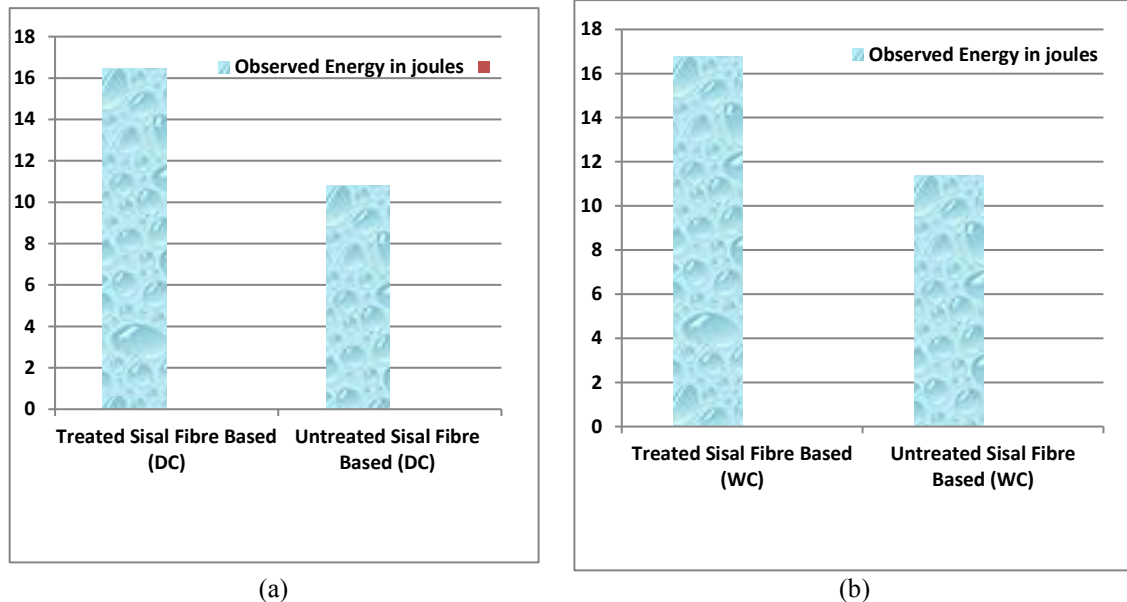


FIGURE 9. Impact Strength of Treated and Untreated Sisal fibre based (a) Dry Composite (DC) (b) Wet Composite (WC)

## CONCLUSION

The natural abundant Sisal and Sisal fibre and one of the artificially strong glass fibre is hydride here with bio resin and hardener matrix to form the hybrid composite panels. In which the Sisal fiber is selectively processed and specially treated for enriching the proposed composite strength. It was experimentally proved that the proposed treated Sisal fibre based composite performed well than untreated Sisal fibre based hybrid composite. Suppose the composite subject to wet condition its performance significantly improved the same was also confirmed by experimental results. Hence the proposed composite is suitable for both dry and wet application. More preferably wet applications.

## REFERENCES

1. T.Gopalakrishnan, Dr.R.Saravanan, B.Musthafa and C.Gnanavel, "Synthesize and exploration of Almond shells – polyester particulate composites", International Journal of Management, Technology and Engineering8, 4515-4525 (2018).
2. Dr.R.Saravanan, T.Gopalakrishnan, B.Musthafa and S.Sivaganesan, "Synthesizing and exploration of tamarind seeds – Epoxy composites", International Journal of Management, Technology and Engineering8, 4526-4535 (2018).
3. R Saravanan and C Gnanavel, "Synthesis and characterization of treated banana fibers and selected jute fiber based hybrid composites", *Materials Today: Proceedings* (2019), <https://doi.org/10.1016/j.matpr.2019.09.143>.
4. Dr.R.Saravanan, M.S.Srinivasa Rao, T.Malyadri and Nagasrisaihari Sunkara, "Synthesize and Characterization of Maleic acid Treated BananaFiber Composites", *Materials Today: Proceedings*18, 5382–5387 (2019).

5. R. Saravanan, T. Gopalakrishnan and P. Jayakrishnamoorthy, "Experimental Investigation of Influence of Sewing Type -Z Axis Reinforcement on Epoxy/Glass Fiber Composite", *Journal of Advances in Mechanical Engineering and Science*, 2, 20-30 (2016).
6. D. Veeman, N. Siva Shanmugam, T. Sathish, V. Petley and G. Sriram, "Experimental Investigation on Plasma Arc Welded Ti64 Sheets", *Transactions of the Canadian Society for Mechanical Engineering* (2019), <https://doi.org/10.1139/tcsme-2019-0149>.
7. T. Sathish, S. Dinesh Kumar, D. Chandramohan, V. Vijayan and R. Venkatesh, "TLONN for the effective prediction of heat transfer rates in tube Heat Exchangers", *Thermal Science, Vinca Institute of Nuclear Sciences* (2019), <https://doi.org/10.2298/TSCI190714438T>.
8. K. Haribabu, M. Sivaprakash, T. Sathish, A. Godwin Antony and V. Vijayan, "Investigation of AC temperature variation by modifying the structure of Passenger car using CFD", *Thermal Science, Vinca Institute of Nuclear Sciences* (2019), <https://doi.org/10.2298/TSCI190409397K>.
9. M. Sivaprakash, K. Haribabu, T. Sathish, S. Dinesh and V. Vijayan, "Support vector machine for modelling and simulation of Heat exchangers", *Thermal Science, Vinca Institute of Nuclear Sciences*, (2019), <https://doi.org/10.2298/TSCI190419398M>.
10. S.P. Palaniappan, K. Muthukumar, R.V.Sabariraj, S.Dinesh Kumar and T. Sathish "CNC Turning process parameters optimization on Aluminium 6082 alloy by using Taguchi and ANOVA", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.10.053.
11. P. Loganathan, M. Dhanashekar, S.Ayyanar, S.R Mohan and T. Sathish, "Mechanical and Wear Behaviour of AA6061/SiC Composites Fabricated by Powder Metallurgy Method", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.10.052.
12. T. Adithiyaa, D. Chandramohan and T. Sathish, "Optimal Prediction of Process Parameters By GWO-KNN in Stirring-Squeeze Casting of AA2219 Reinforced Metal Matrix Composites", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.10.051.
13. K. Gurusami, D. Chandramohan, S. Dinesh Kumar, M. Dhanashekar and T. Sathish, "Strengthening Mechanism of Nd: Yag Laser Shock Peening for Commercially Pure Titanium (CP-Ti) on Surface Integrity and Residual Stresses", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.09.141.
14. K. Muthukumar, R.V Sabariraj, S. Dinesh Kumar and T. Sathish, "Investigation of Thermal Conductivity and Thermal Resistance Analysis on Different Combination of Natural Fiber Composites of Banana, Pineapple and Jute", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.09.140.
15. T. Sathish, S. Dinesh Kumar and S.Karthick, "Modelling and Analysis of Different Connecting Rod Material Through Finite Element Route", *Materials Today Proceedings*, (2019), 10.1016/j.matpr.2019.09.139.
16. M. Swapna Sai, V. Dhinakaran, K.P. Manoj Kumar, V. Rajkumar, B. Stalin and T. Sathish, "A Systematic Review of Effect of Different Welding Process on Mechanical properties of Grade 5 Titanium Alloy", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.09.027.
17. T. Sathish, "Experimental Investigation of Machined Hole and Optimization of Machining Parameters Using Electrochemical Machining", *Journal of Materials Research and Technology* 8 4354-4363 (2019).
18. V. Dhinakaran, M. Varsha Shree, T. Jagadeesha, P.M. Bupathi Ram, T. Sathish and B. Stalin, "A Review on the Recent Developments in Modeling Heat and Material Transfer", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.08.079.
19. G. K. Nagesha, V. Dhinakaran, M.Varsha Shree, K. P. Manoj Kumar, D. Chalawadi and T. Sathish, "Review on characterization and impacts of the lattice structure in additive manufacturing", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.08.158.
20. V. Dhinakaran, J. Ajith, A. Fathima Yasin Fahmidha, T. Jagadeesha, T. Sathish and B. Stalin, "Wire arc additive manufacturing (WAAM) process of nickel based superalloys- a Review", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.08.159.
21. T. Adithiyaa, D. Chandramohan and T. Sathish, "Flower Pollination Algorithm for the Optimization of Stair casting parameter for the preparation of AMC", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.07.711.
22. S. Dinesh Kumar, D. Chandramohan, K. Purushothaman and T. Sathish, "Optimal Hydraulic And Thermal Constrain For Plate Heat Exchanger Using Multi Objective Wale Optimization", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.07.710.
23. R. Praveen Kumar, P. Periyasamy, S. Rangarajan and T. Sathish, "League Championship Optimization for the Parameter selection for Mg/WC Metal", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.06.646.

24. T. Sathish, S. Dinesh Kumar, K. Muthukumar and S. Karthick, "Temperature Distribution Analysis on Diffusion Bonded Joints of Ti-6Al-4V with AISI 4140 Medium Carbon Steel", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.07.60.
25. T. Sathish, S. Dinesh Kumar, K. Muthukumar and S. Karthick, "Natural Inspiration Technique for the Parameter Optimization of A-GTAW Welding of Naval Steel", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.07.600.
26. A. Parthiban, V. Vijayan, S. Sathish and T. Sathish, "Optimization of CO<sub>2</sub> Laser cutting parameter on motor cycle frame materials", *International Journal of Recent Technology and Engineering* 8 409-412 (2019).
27. R. Praveen Kumar, P. Periyasamy, S. Rangarajan and T. Sathish, "Comparison of Mechanical and Tribological Behaviour of Magnesium in composition with various Metal", *International Journal of Recent Technology and Engineering* 8, 947-950 (2019).
28. S.Dinesh Kumar, K.Purushothaman, D.Chandramohan, M.MohinishDushyantraj and T. Sathish, "ANN-AGCS for the prediction of temperature distribution and required energy in hot forging process using finite element analysis", *Materials Today Proceedings* (2019),10.1016/j.matpr.2019.05.426.
29. T. Sathish, S. Rangarajan, A. Muthuram and R. Praveen Kumar, "Analysis and Modelling of Dissimilar Materials Welding based on K-Nearest Neighbour Predictor", *Materials Today Proceedings* (2019), 10.1016/j.matpr.2019.05.371.
30. T. Sathish, S. Saravanan, and V. Vijayan, "Effect of Reinforced Aluminum Alloy LM30 with pure ceramic particles to evaluate hardness and wear properties", *Materials Research Innovations* (2019), 10.1080/14328917.2019.1614321.
31. K. Gurusami, K. Shanmuga Sundaram, D. Chandramohan, S. Dinesh Kumar, P. Vasantha Srinivasan, and T. Sathish, "A Comparative Study on Surface Strengthening Characterization and Residual Stresses of Dental Alloys using Laser Shock Peening", *International Journal of Ambient Energy* (2019), 10.1080/01430750.2019.1614987.
32. T. Sathish, "Optimization of Co<sub>2</sub> laser cutting parameters on Austenite stainless steel using Gray Relational Analysis", *International Journal of Mechanical Engineering and Technology* (2019), 10, 984-992 (2019).
33. T. Sathish, "A study of Temperature Distribution on 3D Printed Component (Piston Ring) and 3D Printer", *International Journal of Mechanical and Production Engineering Research and Development* 9, 547-553 (2019).
34. T. Sathish, "Influence of Surface Roughness in Turning Process-an Analysis Using Artificial Neural Network", *Transactions of the Canadian Society for Mechanical Engineering*, 43, 509-514 (2019).
35. T. Sathish, "An Experimental investigation on Thermal Bonded Joints of Ti-6Al-4V With SS304L", *International Journal of Mechanical and Production Engineering Research and Development*, 9, 554-561 (2019).
36. T. Sathish, "Profit Maximization in Reverse Logistic based on Disassembly Scheduling using Hybrid Bee Colony Bat Optimization", *Transactions of the Canadian Society for Mechanical Engineering* 43, 551-559 (2019).
37. T. Sathish, "Equivalent stress prediction of Automobile structural member using FEA-ANN Technique", *International Journal of Mechanical and Production Engineering Research and Development*, 9, 757-768 (2019).
38. T. Sathish, "Fluid Flow analysis of composite material based wind turbine blades using ANSYS", *International Journal of Ambient Energy* (2019) 10.1080/01430750.2019.1608861.
39. T. Sathish, "Artificial Intelligence Based Green Manufacturability quantification of a unit production process", *International Journal of Mechanical and Production Engineering Research and Development* 9, 841-852 (2019).
40. Dr. J. Jayaprakash, N. Thinakaran and T. Sathish, "JADE implementation of Multi-agent based Inventory routing problem", *International Journal of Applied Engineering Research*, 9 28785-28792 (2014).
41. T. Sathish, and J. Jayaprakash, "Meta-Heuristic Approach to Solve Multi Period Disassembly-To-Order Problem of End-Of-Life Products using Adaptive Genetic Algorithm", *International Journal of Mechanical & Mechatronics Engineering* 15, 59-67 (2015).
42. T. Sathish, J. Jayaprakash, P.V. Senthil and R. Saravanan, "Multi Period Disassembly-to-Order of End of Life Product based on scheduling to maximize the Profit in Reverse Logistic Operation", *FME Transactions* 45, 172-180 (2017)
43. T. Sathish, "Effect of Welding parameters on Mechanical Properties of plasma Transferred Arc Welded SS 202 Plates", *Applied Mechanics and Materials*, 852 324-330 (2016).

44. T. Sathish, J. Jayaprakash, "Meta – Heuristic Approach to Solve Multi Period DTO Problem of EOL Products", *International Journal of Logistics Systems and Management* 26 59-67 (2017).
45. T. Sathish, "Microstructure and Mechanical Properties of hard ceramic particulate reinforced AA 7075 Alloy composites Via liquid metallurgy route", *Materials Today Proceedings* 5, 26860-26865 (2018).
46. T. Sathish, "Checking the mechanical properties of Ananascomosus Leaf fiber reinforced polymer composite Material", *International Journal of Pure and Applied Mathematics* 116, 243-253 (2017).
47. T. Sathish, "Performance Measurements on Extracted Bio-Diesel from waste plastic", *Journal of Applied Fluid Mechanics* 10, 41-50 (2017).
48. T. Sathish, "Heat Transfer Analysis of Nano-Fluid Flow in a converging Nozzle with different aspect Ratios", *Journal of New Materials for Electrochemical Systems* 20, 161-167 (2017).
49. T. Sathish, "Optimizing Supply Chain in Reverse Logistics", *International Journal of Mechanical and Production Engineering Research and Development* 7 551-560 (2017).
50. T. Sathish, "Design and simulation of connecting rods with several test cases using AL alloys and high Tensile steel", *International Journal of Mechanical and Production Engineering Research and Development* 8, 1119-1126 (2018).
51. T. Sathish, "GAC-ANN Technique for Prediction of Spring Back Effect in Wipe Bending Process of Sheet Metal", *Materials Today Proceedings* 5, 14448-14457 (2018).
52. T. Sathish, "BONN Technique: Tribological Properties Predictor for Plasma Nitrided 316L Stainless Steel", *Materials Today Proceedings* 5, 14545-14552 (2018).
53. T. Sathish, "Design and Fabrication of Industrial Components Using 3D Printing", *Materials Today Proceedings* 5 14489-14498 (2018).
54. T. Sathish, "BCCS Approach for the Parametric Optimization in Machining of Nimonic-263 alloy using RSM", *Materials Today Proceedings* 5, 14416-14422 (2018).
55. T. Sathish, "HAIWF based fault detection and classification for Industrial Machine Condition Monitoring", *Progress in Industrial Ecology* 12, 46-58 (2018).
56. T. Sathish, "Prediction of Springback Effect by the Hybridization of ANN with PSO in Wipe Bending process of sheet Metal", *Progress in Industrial Ecology* 12, 112-119 (2018).
57. T. Sathish, "IWF Based Optimization of Porous Insert Configurations for Heat Transfer Enhancement Using CFD", *Journal of Applied Fluid Mechanics* 11, 31-37 (2018).
58. T. Sathish, "Modelling of Manhattan K-Nearest Neighbor for Exhaust Emission Analysis of CNG-Diesel Engine", *Journal of Applied Fluid Mechanics* 11, 39-44 (2018).
59. T. Sathish, "An Extensive Review of Reverse Logistics and its Benefits in supply chain Management", *International Journal of Mechanical and Production Engineering Research and Development* 165-178 (2018).
60. T. Sathish, "Investigation on structural and Thermal analysis of disc brake with Aluminium Metal Matrix Composite", *International Journal of Mechanical and Production Engineering Research and Development* 431-440 (2018)
61. T. Sathish, "A Review on Mechanical and Tribological Behaviour of Aluminium based Metal Matrix Composites", *International Journal of Mechanical and Production Engineering Research and Development* 473-478 (2018).
62. T. Sathish, "Ocean Wave Energy Scenario in India", *International Journal of Mechanical and Production Engineering Research and Development* 582-590 (2018).
63. T. Sathish, "Experimental investigation on degradation of heat transfer properties of a black chromium-coated aluminium surface solar collector tube", *International Journal of Ambient Energy* 39, <https://doi.org/10.1080/01430750.2018.1492456>.
64. T. Sathish, "Modelling of cost based optimization system E-O-L Disassembly in Reverse Logistics", *International Journal of Mechanical and Production Engineering Research and Development* 711-716 (2018).
65. T. Sathish, "Modelling K-Nearest Neighbour technique for the parameter prediction of cryogenic treated tool in surface rough minimization", *International Journal of Mechanical and Production Engineering Research and Development* 705-710 (2018).
66. T. Sathish, "Modelling of HCHS system for optimal E-O-L Combination section and Disassembly in Reverse Logistics", *Applied Mathematics and Information science* 13, 1-6 (2019).
67. T. Sathish, "Performance Analysis in End Milling operation", *International Journal of Mechanical Engineering and Technology* 9, 2263-2271 (2018).
68. T. Sathish, "Comparison of Different Tool path in Pocket Milling", *International Journal of Mechanical Engineering and Technology*, 9, 922-927 (2018).

69. T. Sathish, "Modelling of support vector Mechanism for green Manufacturability Quantification of Production", [Lecture notes on Mechanical Engineering](https://doi.org/10.1007/978-981-13-6374-0_45) (2019), [https://doi.org/10.1007/978-981-13-6374-0\\_45](https://doi.org/10.1007/978-981-13-6374-0_45).
70. T. Sathish, "A Study on Making of Compact Manual Paper Recycling Plant for Domestic Purpose", *International Journal of Mechanical and Production Engineering Research and Development* 8, 1515-1535 (2018).