

Journal Pre-proofs

Original article

Novel Marine *Nocardiopsis dassonvillei*- DS013 Mediated Silver Nanoparticles Characterization and its Bactericidal Potential against Clinical Isolates

Suresh Dhanaraj, Somanathan Thirunavukkarasu, Henry Allen John, Sridhar Pandian, Saleh H. Salmen, Arunachalam Chinnathambi, Sulaiman Ali Alharbi

PII: S1319-562X(20)30004-8
DOI: <https://doi.org/10.1016/j.sjbs.2020.01.003>
Reference: SJBS 1563

To appear in: *Saudi Journal of Biological Sciences*

Received Date: 30 October 2019
Revised Date: 29 December 2019
Accepted Date: 6 January 2020



Please cite this article as: S. Dhanaraj, S. Thirunavukkarasu, H. Allen John, S. Pandian, S.H. Salmen, A. Chinnathambi, S. Ali Alharbi, Novel Marine *Nocardiopsis dassonvillei*- DS013 Mediated Silver Nanoparticles Characterization and its Bactericidal Potential against Clinical Isolates, *Saudi Journal of Biological Sciences* (2020), doi: <https://doi.org/10.1016/j.sjbs.2020.01.003>

This is a PDF file of an article that has undergone enhancements after acceptance, such as the addition of a cover page and metadata, and formatting for readability, but it is not yet the definitive version of record. This version will undergo additional copyediting, typesetting and review before it is published in its final form, but we are providing this version to give early visibility of the article. Please note that, during the production process, errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

© 2020 Published by Elsevier B.V. on behalf of King Saud University.

Novel Marine *Nocardiopsis dassonvillei*- DS013 Mediated Silver Nanoparticles Characterization and its Bactericidal Potential against Clinical Isolates

Suresh Dhanaraj¹, Somanathan Thirunavukkarasu², Henry Allen John¹, Sridhar Pandian³, Saleh H. Salmen⁴, Arunachalam Chinnathambi^{4*}, Sulaiman Ali Alharbi^{4*}

¹School of Life Sciences, Department of Microbiology, Vels Institute of Science, Technology, and Advanced Studies (VISTAS), Pallavaram, Chennai, 600 117 Tamil Nadu, India.

²School of Basic Sciences, Department of Chemistry, Vels Institute of Science, Technology, and Advanced Studies (VISTAS), Pallavaram, Chennai, 600 117 Tamil Nadu, India.

³PG and Research Department of Biotechnology, Sengunthar Arts and Science College, Tiruchengode, Namakkal, 637 205, Tamil Nadu, India.

⁴Department of Botany and Microbiology, College of Science, King Saud University, Riyadh 11451 Saudi Arabia.

***Corresponding author Email: carunachalam@ksu.edu.sa; sharbi@ksu.edu.sa;**

Novel Marine *Nocardiopsis dassonvillei*- DS013 Mediated Silver Nanoparticles Characterization and its Bactericidal Potential against Clinical Isolates

Abstract

The sediment marine samples were obtained from several places along the coastline of the Tuticorin shoreline, Tamil Nadu, India were separated for the presence of bioactive compound producing actinobacteria. The actinobacterial strain was subjected to 16Sr RNA sequence cluster analysis and identified as *Nocardiopsis dassonvillei*- DS013 NCBI accession number: KM098151. Bacterial mediated synthesis of nanoparticles gaining research attention owing its wide applications in nonmedical biotechnology. In the current study, a single step eco-friendly silver nanoparticles (AgNPs) were synthesized from novel actinobacteria *Nocardiopsis dassonvillei*- DS013 has been attempted. The actinobacterial mediated silver nanoparticles were characterized by TEM, UV-Visible, XRD, FT-IR spectroscopy. The initial detection of AgNPs was identified using UV-Vis spectrum and confirmed by the appearance of absorbance peak at 408 nm. A Fourier transform infrared spectroscopy (FT-IR) result reveals the presence of protein component in the culture supernatant may act as protecting

agents. The XRD pattern indicated that the typical peaks reveal the presence of nanoparticles. The TEM morphology confirms the formation of circular and non uniform distributions of AgNPs with the size range from 30-80 nm. The antibacterial activity of both isolated actinobacterial (IA) and silver nanoparticles mediated actinobacterial (SNA) of *Nocardioopsis dassonvillei*- DS013 were done by well diffusion method against selected clinical isolates of bacteria, namely *Escherichia coli*, *Enterococcus* sp., *Pseudomonas* sp., *Klebsiella* sp., *Proteus* sp., *Shigella* sp., *Bacillus subtilis*, and *Streptococcus* sp. When compared to isolated actinobacteria, the SNA shows the better antibacterial activity against clinical isolates.

Keywords *Nocardioopsis dassonvillei*, Marine actinobacteria, AgNPs, Marine sediments.

Introduction

Existence of multidrug resistance pathogens in the environment is a serious problem around the globe. Which may cause different types of diseases and occasionally fatal to humans (Sondi and Salopek-Sondi, 2004; Pal et al., 2007; Ingle, et al., 2008; Bonde, et al., 2012; Begum, et al., 2013; Gupta et al., 2013; Rai, et al., 2015; Singh, et al., 2015). To overcome this problem, there is a demand to find effective, affordable, and safe antimicrobials from the microorganisms present in the natural environment. Actinobacteria belong to the Gram-positive, free-living, saprophytic, filamentous bacteria that abound in the environment producing numerous well documented biologically active secondary metabolites having potential to be used as novel antibiotics that may have a significant role in therapeutic applications. They are predominantly associated with almost all soil, fresh water and marine environments (Gebreyohannes, et al., 2013). The diverse group of marine actinobacteria has mostly been unexplored and thereby remains elusive. The highly complex marine environments prevalent in various regions were found to be like high pressures, varying salinity and diverse temperature zones in natural habitats that have resulted in the development of diversified group of microorganisms colonizing these ecological niches

(Olano, et al., 2009). The adaptation and survival of the marine actinobacteria in a complex ecosystem has been considerably linked to the inherent ability of the diversified group of actinobacteria that predominantly produce secondary metabolites with antibacterial activity. In this context, marine sediments have continuously been at the forefront as a prospective source for isolation of actinobacteria which may yield novel antimicrobial compounds (Goodfellow et al., 2013). Comparatively DNA of actinobacteria has higher percentage of GC bases. The highly conserved 16s rRNA encoding genes are regularly used as genetic markers to determine the taxonomy, phylogeny and species divergence rates among bacteria, and 16s rRNA sequence analysis should be used to construct phylogenetic trees for microorganisms (Manojkumar and Subbaiya, 2016). Screening and utilization of marine actinobacteria in bio nanotechnology has significant attention (Sadhasivam, et al., 2010; Sadhasivam, et al., 2012), which exhibit various effective and potential applications in drug delivery, cancer therapy, etc., (Willets et al., 2007; Gittins, et al., 2000; Jain et al., 2007). Recent focus has been on eco-friendly methods for the green synthesis of metal nanoparticles utilizing biomaterials (Kowshik, et al., 2002; Senapati, et al., 2005; Shahverdi, et al., 2007). Many researchers have reported the effect of microbial mediated AgNPs against several multidrug resistant microbes (Chaudhari, et al., 2012; Priyaragini, et al., 2013; Saminathan, 2015). Previous investigator (Sastry, et al., 2003) observed the antimicrobial and cytotoxic effects utilizing AgNPs from a newly isolated *Nocardiopsis* sp. MBRC. In this communication we report a single step eco synthesis of silver nanoparticles using novel actinobacteria *Nocardiopsis dassonvillei*-DS013 isolated and reported for the first time from marine sediments coastline of the Tuticorin shoreline, Tamil Nadu, India. The actinobacterial mediated AgNPs was utilized to study their antibacterial activities towards selected clinical bacterial isolates such as *Escherichia coli*, *Enterococcus* sp., *Pseudomonas* sp., *Klebsiella* sp., *Proteus* sp., *Shigella* sp., *Bacillus subtilis*, and *Streptococcus* sp.

Materials and Methods

Collection of Marine Sediments

Marine sediments were obtained in depth not more than 10 to 15 cm from 11 different places at intervals of 500 m from the coastline of Tuticorin, Tamil Nadu, India. The marine soil sediment samples from each of the locations were aseptically placed in sterile wide mouthed sample collection jars, appropriately labelled, stored in icebox and taken to the laboratory

within 12 hours. The materials were preserved by refrigeration, where required, until further processing. The sediment samples were air-dried for one week. The air-dried samples were sieved – using 1mm mesh; and the fine grain samples were stored for pre-treatment in a hot air oven at 50°C for 60 min. The dried marine soil sediment was then used for screening of actinobacteria.

Isolation of Actinobacteria from marine sediments

Screening of actinobacteria from marine soil sediment sample was done by spread plate method (Manivasagan, et al., 2013). The soil suspension was subjected to standard serial decimal dilution to give dilutions of 10^{-1} to 10^{-10} using sterile 0.9% saline as diluents (Vimal, et al., 2009). The actinobacteria from treated marine sediment samples was isolated by standard spread plating on the surface Starch Casein Agar (SCA; Hi-Media, India) (Selvakumar, et al., 2012) supplemented with cycloheximide (25mg/mL; SCAC) (Sivakumar, et al., 2007) in level 1 bio safety cabinet. The whole procedure for each sample was done in triplicates to maximize the chance of isolating actinobacteria. The plates were dried for 25 min and incubated at 30°C (4 weeks). Colonies showing typical actinobacteria growth characteristics were preserved by sub-culture on Yeast Extract Malt Extract Agar (Hi-Media) and stored under refrigerated conditions until further use.

Identification of Actinobacteria by 16s rRNA Sequencing

DNA Isolation

The isolated actinobacteria from marine sediments was aseptically transferred in Starch Casein Broth and incubated at 37°C for 6 days. After obtained the significant growth ($OD_{590} \leq 0.9$) the culture tube was centrifuged at 10,000 rpm for 15 min to separate the fungal mycelium. About 0.1g of mycelium was crushed with the help of liquid nitrogen. With addition of 50 μ l TE buffer and 20mg/ml of lysozyme the tube was incubated at 30°C for 30 min. Later, the tube was added with each 20 μ l of 10% SDS and proteinase K and kept for incubation at 50°C for 30 min. The solution of Phenol - chloroform was added in 1:1 ratio and centrifuged at 10,000 rpm for 5.0 min to extract lysate. The upper layer solution was transferred into a new eppendorf tube and ethanol precipitation was carried out to separate the DNA using 70% of ethanol and then the tubes were kept for incubation at -20°C for 30 min. To obtain the pellet the tubes were centrifuged at 10,000 rpm for 15 min and gently washed with 90% of ethanol before it suspended in 25 μ l of TE buffer. The 20 μ l RNase was added in

the mixer tube and it was incubated at 37°C for 1.0 h. The phenol chloroform extraction procedure was carried out to acquire pure product of nucleic acid (Saurav, et al., 2010).

PCR Amplification and Sequencing

Molecular identification procedure includes isolation and genomic DNA extraction, 16S rRNA amplification, PCR product purification, PCR amplicon gene product sequencing was performed in Acme Progen Biotech (India) Pvt. Ltd, Salem, Tamil Nadu, India. PCR amplification of the 16s rRNA was achieved by adding final volume of the reaction mixture 25µl includes PCR buffer (1X), MgCl₂ (1.5 mM), Deoxyribonucleotide triphosphate dNTP (200µM), primers 20 pmol, 2.5U *Thermus aquaticus* DNA polymerase and 100 ng of DNA template. The PCR amplification was carried out in Eppendorf Thermocycler 96. The 30 cycles of PCR was carried out at the temperature of 94°C for 1.0 min, 55°C for 1.0 min. and 72 °C for 2.0 min. The PCR amplicon product was detected by electrophoresis - using 1.0% of agarose gel in Tris/Borate/EDTA buffer pH 8.5; at 150 V for 25 min, stained with ethidium bromide and visualized under ultraviolet transilluminator (Vijayakumar, et al., 2010). The gel image was took using gel documentation and analysed. Later, the PCR amplicon products were eluted by the method given in Gel elution kit. In later PCR purification kit (Qiagen, Germany) were used to purify the elution mixture and finally the DNA sequences were obtained using an ABI xl 3730 DNA analyzer, Applied Biosystems. The obtained sequences were submitted to the NCBI and based upon the maximum score among the other organisms the query organism was confirmed.

Synthesis of Silver nanoparticles using *Nocardiopsis dassonvillei*-DS013

About 3.0ml culture of *Nocardiopsis dassonvillei*-DS013 was added into 47ml of Silver nitrate (AgNO₃) solution separately with continuous stirring the solution. The colour has transformed from pale yellow to dark brown color which illustrates the presence of SNPs (Heuer, et al., 1997). The silver nanoparticles mediated actinobacterial (SNA) were studied by UV-Vis spectroscopy, XRD, FT-IR and TEM.

Antibacterial Activity

The antibacterial activity of isolated actinobacterial (IA) and silver nanoparticles mediated actinobacterial (SNA) were evaluated by using well diffusion method described by (Naganathan, and Thirunavukkarasu, 2017). In brief: sterile Mueller Hinton Agar (MHA; Hi-

Media) plates were swabbed with overnight Mueller-Hinton Broth culture of any one of the selected test organism with approximately 10^6 CFU per ml - turbidity standard equal to 0.5 and 1.0 McFarland standard for Gram negative bacteria and Gram positive bacteria, respectively and labelled appropriately. The plates were dried for 25 min and 4.0 wells of 5.0mm diameter were formed by utilizing sterile borer on MHA. The IA and SNA were cultivated in 50 mL Starch Casein Broth for 72 hrs at 30°C and the culture filtrates were obtained by filtration through 45µm membrane filter (Sartorius). 100µl of culture filtrate from IA and SNA was respectively loaded into labelled well and incubated in upright position for 30 min and further incubated at 35°C for 16-18 h. The results for preliminary screening of antibacterial activity by IA and SNA against test bacteria, if any, measured as zone of inhibition in mm and recorded.

Results and Discussion

Isolation of Actinobacteria from Marine soil sediment

After incubation, a distinct actinobacteria were isolated and identified based on the appearance of powdery colonies from marine soil sediment samples collected from the Bay of Bengal along Tuticorin shoreline, Tamil Nadu, India. Based on characteristic appearance the strains of actinobacteria were purified by streak plate method using (SCA) Starch Casein Agar. Among the diverse groups of microbes in marine ecosystem, Actinobacteria have a significant niche as a prospective producer of distinctive metabolites and biological active compounds (Ganesan, et al., 2017). Similarly, previous investigator Rathod et al., (2016) reported first time about the isolation of alkaliphilic actinobacterium *N. valliformis* OT1 strain from Central India, synthesis of AgNPs and its antibacterial activity against bacterial pathogens (Abirami, and Kannabiran, 2016).

Molecular identification of *Nocardiopsis dassonvillei*-DS013 by 16s rRNA sequencing

The marine actinobacteria was identified as *Nocardiopsis dassonvillei*-DS013 based on the morphological, physiological, and various biochemical characteristics and also it was confirmed by 16s rRNA sequencing. The obtained DNA (genomic) was amplified and the PCR amplicon gene product (**Fig. 1**) was detected in 1.0% agarose gel with 1.0kb ladder used as marker and determined that the amplicon was not degraded. The PCR amplified product yielded the molecular size of DNA 1.5 kb in length (**Fig. 2**). The automated sequencer was used to retrieve the sequence with help of appropriate primers. The obtained sequence was submitted to GenBank in NCBI with the accession number (**KM098151**).

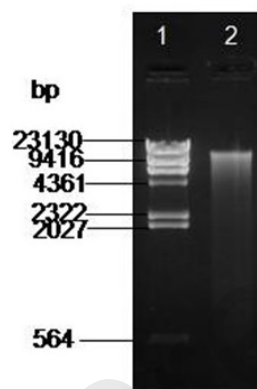


Fig. 1 Agarose Gel (1.0%) showing (1) Lambda DNA/HindIII Digest Marker and (2) Genomic DNA product of *Nocardiopsis dassonvillei*-DS013

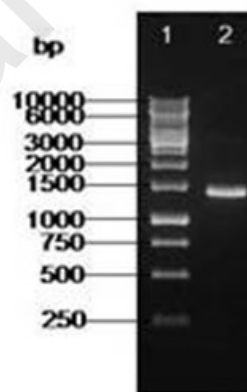


Fig. 2 Agarose Gel (1.0%) showing (1) Lambda 1Kb DNA ladder and (2) PCR product of *Nocardiopsis dassonvillei*-DS013

Characterization of silver nanoparticle obtained from *Nocardiopsis dassonvillei*-DS013

UV-Vis spectrum of SNA

Fig. 3 illustrates the UV-Visible spectrum of AgNPs mediated *Nocardiopsis dassonvillei*-DS013, which shows absorbance peak at 408 nm. This is because of the effect of surface plasmon resonance intense peak. Nonappearance of peaks between 300 and 560 nm which clearly indicates the formed nanoparticles are without aggregation (Rathod, et al., 2016; Banerjee, et al., 2018; Balashanmugam, et al., 2013).

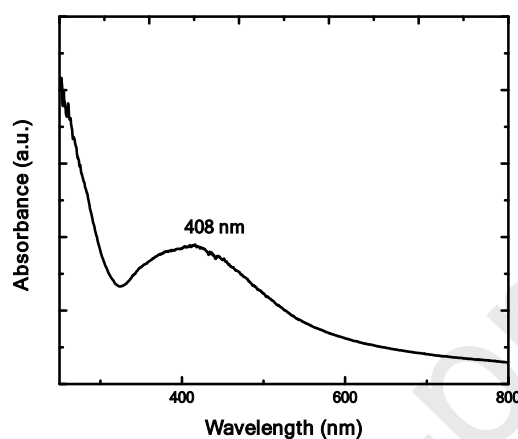


Fig.3 UV-Visible Spectrum of SNA

XRD Analysis of SNA

XRD pattern of SNA show intensive peaks at $2\theta = 37.10^\circ$, 42.10° , 59.42° and 69.21° these indexed peaks are (111), (200), (220) and (311) lattice, respectively (**Fig.4**). AgNPs The indexed plane indicates the FCC structure of Ag.

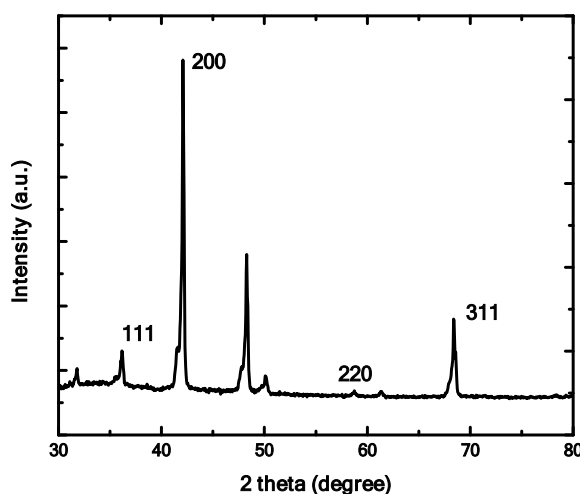


Fig.4 XRD pattern of SNA

FTIR Analysis of SNA

To understand the contribution of the bio molecules which reduces the Ag^+ ions into AgNPs, the FT-IR spectroscopy was performed. **Fig.5** represents the FT-IR spectrum of SNA, the absorbance peaks at 3336 cm^{-1} and 3370 cm^{-1} leads to the extending OH groups of vibrations. A strong peaks of 1574 cm^{-1} relates the extending vibration of $\text{C}=\text{O}$ which affirms the formation of AgNPs of *Nocardiopsis dassonvillei*-DS013. A peaks at 653 cm^{-1} and 504 cm^{-1} relates to extending vibration of $\text{C}-\text{Cl}$ and $\text{C}-\text{Br}$ bond, respectively. The strong broad absorbance at 653 cm^{-1} is the characteristics of alkynes group (Verma, et al., 2014; Sivalingam, et al., 2012; Kumar, et al., 2011).

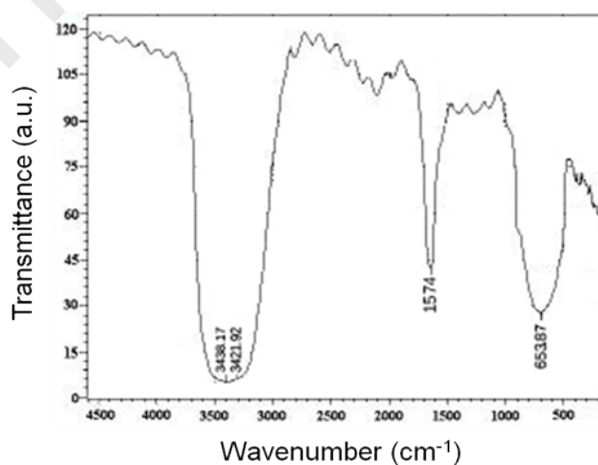


Fig.5 FTIR analysis of SNA

TEM Image of SNA

Fig.6 shows the TEM image of AgNPs mediated *Nocardiopsis dassonvillei*-DS013 with circular in morphology with non uniform distributions in the dimension range of 30-80 nm. The obtained results were correlated among previous investigations (Krishnaraj, et al., 2010; Shahverdi, et al., 2007).

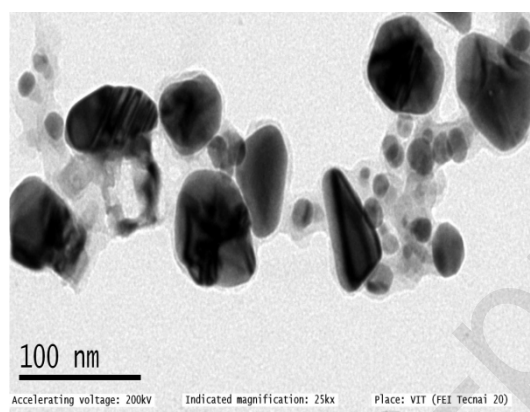


Fig.6 TEM analysis of SNA

Antibacterial potential of IA and SNA of *Nocardiopsis dassonvillei*-DS013 against tested clinical isolates of bacteria

In this work, the antibacterial activity of silver nanoparticles mediated actinobacterial (SNA) were assessed against the selected clinical isolates of bacteria such as *Escherichia coli*, *Enterococcus* sp., *Pseudomonas* sp., *Klebsiella* sp., *Proteus* sp., *Shigella* sp., *Bacillus subtilis*, and *Streptococcus* sp. In this assessment the most interesting results were observed that SNA had the highest activity showing remarkable activity against all test organisms compare to IA. The IA from marine sediment demonstrated slight (1.0 – 8.0 mm) antibacterial activity and SNA showed the moderate to maximum activity (more than 13 mm) against all clinical isolates as determined by zone diameter in mm (Table 1) this is because of the reduction of

size of Ag⁺ to Ag⁰ utilizing the marine actinobacteria (Kalishwaralal, et al., 2008; Manivasagan, et al., 2013) (Kalishwaralal, et al., 2008; Manivasagan, et al., 2013).

Table.1: Showing antibacterial activity of IA and SNA against clinical bacterial isolates

Clinical bacterial isolates	Antibacterial activity of IA and SNA strain	
	Zone diameter (mm)	
	IA	SNA
<i>E. coli</i>	4	14
<i>Enterococcus</i> sp.,	0	18
<i>Pseudomonas</i> sp.,	0	15
<i>Klebsiella</i> sp.,	3	24
<i>Proteus</i> sp.,	2	16
<i>Bacillus subtilis</i> sp.,	2	18
<i>Shigella</i> sp.,	2	13
<i>Streptococcus</i> sp.,	9	17

IA- Isolated Actinobacteria; SNA- Silver Nanoparticles Mediated Actinobacteria

Conclusions

All among the microorganisms in the marine ecosystem; marine actinomycetes have a highest metabolic and genetic diversity. An exceptional perceives and efforts are need to explore on marine actinobacteria as source for the novel metabolites. Actinomycetes not only exist in the ocean, but also widely present in the different marine ecosystem. Precious secondary metabolites from marine actinomycetes and its potential should not be overlooked. In the present study we isolated and identified a novel marine actinobacteria *Nocardiopsis dassonvillei*-DS013 present in the soil sediments from different places along the coastline of the Bay of Bengal along the Tuticorin shoreline, Tamil Nadu, India. The marine actinobacteria *Nocardiopsis dassonvillei*-DS013 mediated AgNPs was synthesised. The XRD

indexed plane indicates the FCC structure of AgNPs and further the structure and size of the synthesized SNA were confirmed by TEM which clearly indicates the dimension range of 30-80 nm with circular in morphology with non uniform distributions. Compared to isolated actinobacteria (IA), the AgNPs mediated marine actinobacteria (SNA) showed excellent antibacterial activity against the various selected clinical isolates of bacteria such as *Escherichia coli*, *Enterococcus* sp., *Pseudomonas* sp., *Klebsiella* sp., *Proteus* sp., *Shigella* sp., *Bacillus subtilis*, and *Streptococcus* sp. From this work we have recognized that the single step eco – synthesis of AgNPs from marine actinobacteria *Nocardiopsis dassonvillei*-DS013 which plays a crucial role in bionanomedicine applications.

Acknowledgements: This project was supported by Researchers Supporting Project number (RSP-2019/5) King Saud University, Riyadh, Saudi Arabia.

References

- Sondi, I., and Salopek-Sondi, B., 2004. Silver nanoparticles as antimicrobial agent: a case study on *E. coli* as a model for Gram-negative bacteria. *J. Colloid. Interface. Sci.* 275(1), 177-182.
- Pal, S., Tak, Y. K., Song, J. M., 2007. Does the antibacterial activity of silver nanoparticles depend on the shape of the nanoparticle? A study of the gram-negative bacterium *Escherichia coli*. *Appl. Environ. Microbiol.* 73(6), 1712-1720.
- Ingle, A., Gade, A., Pierrat, S., Sonnichsen, C., Rai, M., 2008. Mycosynthesis of silver nanoparticles using the fungus *Fusarium acuminatum* and its activity against some human pathogenic bacteria. *Curr. Nanosci.* 4(2), 141-144.

Bonde, S. R., Rathod, D. P., Ingle, A. P., Ade, R. B., Gade, A. K., Rai, M. K., 2012. Murraya koenigii-mediated synthesis of silver nanoparticles and its activity against three human pathogenic bacteria. *Nanosci. Method.* 1(1), 25-36.

Begum, S., Hasan, F., Hussain, S., Shah, A. A., 2013. Prevalence of multi drug resistant *Acinetobacter baumannii* in the clinical samples from Tertiary Care Hospital in Islamabad, Pakistan. *Pak. J. Med. Sci.* 29(5), 1253.

Gupta, A., Bonde, S. R., Gaikwad, S., Ingle, A., Gade, A. K., Rai, M., 2013. Lawsonia inermis-mediated synthesis of silver nanoparticles: activity against human pathogenic fungi and bacteria with special reference to formulation of an antimicrobial nanogel. *IET Nano. Biotechnol.* 8(3), 172-178.

Rai, M., Ingle, A. P., Gade, A. K., Duarte, M. C. T., Duran, N., 2015. Three Phoma spp. synthesised novel silver nanoparticles that possess excellent antimicrobial efficacy. *IET Nano. Biotechnol.* 9(5), 280-287.

Singh, A., Prasad, K. N., Misra, R., Rahman, M., Singh, S. K., Rai, R. P., Srivastava, J. K., 2015. Increasing trend of heterogeneous vancomycin intermediate *Staphylococcus aureus* in a Tertiary Care Center of Northern India. *Microb. Drug. Resist.* 21(5), 545-550.

Gebreyohannes, G., Moges, F., Sahile, S., Raja, N., 2013. Isolation and characterization of potential antibiotic producing actinomycetes from water and sediments of Lake Tana, Ethiopia. *Asian. Pac. J. Trop. Biomed.* 3(6), 426-435.

Olano, C., Méndez, C., Salas, J., 2009. Antitumor compounds from marine actinomycetes. *Mar. Drugs.* 7(2), 210-248.

Goodfellow, M., Brown, R., Ahmed, L., Pathom-Aree, W., Bull, A. T., Jones, A. L., Wang, J., 2013. *Verrucosipora fiedleri* sp. nov., an actinomycete isolated from a fjord sediment which synthesizes proximicins. *Anton. Leeuw. Int. J.* 103(3), 493-502.

Manojkumar, S., and Subbaiya, R., 2016. Isolation and Identification of Soil derived Actinomycetes *Nocardiosis alba*. *Res. J. Pharm. Biol. Chem. Sci.* 7(3), 485-493.

Sadhasivam, S., Shanmugam, P., Yun, K., 2010. Biosynthesis of silver nanoparticles by *Streptomyces hygroscopicus* and antimicrobial activity against medically important pathogenic microorganisms. *J. Colloid. Interface. Sci.* 81(1), 358-362.

Sadhasivam, S., Shanmugam, P., Veerapandian, M., Subbiah, R., Yun, K., 2012. Biogenic synthesis of multidimensional gold nanoparticles assisted by *Streptomyces hygroscopicus* and its electrochemical and antibacterial properties. *Biometals.* 25(2), 351-360.

Willems, K. A., & Van Duyne, R. P., 2007. Localized surface plasmon resonance spectroscopy and sensing. *Annu. Rev. Phys. Chem.* 58, 267-297.

Gittins, D. I., Bethell, D., Schiffrin, D. J., Nichols, R. J., 2000. A nanometre-scale electronic switch consisting of a metal cluster and redox-addressable groups. *Nature.* 408 (6808), 67.

Jain, P. K., El-Sayed, I. H., El-Sayed, M. A. 2007. Au nanoparticles target cancer. *Nano. Today*. 2(1), 18-29.

Kowshik, M., Ashtaputre, S., Kharrazi, S., Vogel, W., Urban, J., Kulkarni, S. K., Paknikar, K. M., 2002. Extracellular synthesis of silver nanoparticles by a silver-tolerant yeast strain MKY3. *Nanotech*. 14(1), 95.

Senapati, S., Ahmad, A., Khan, M. I., Sastry, M., Kumar, R., 2005. Extracellular biosynthesis of bimetallic Au–Ag alloy nanoparticles. *Small*. 1(5), 517-520.

Shahverdi, A. R., Minaeian, S., Shahverdi, H. R., Jamalifar, H., Nohi, A. A., 2007. Rapid synthesis of silver nanoparticles using culture supernatants of Enterobacteria: a novel biological approach. *Process. Biochem*. 42(5), 919-923.

Chaudhari, P. R., Masurkar, S. A., Shidore, V. B., Kamble, S. P., 2012. Effect of biosynthesized silver nanoparticles on *Staphylococcus aureus* biofilm quenching and prevention of biofilm formation. *Nano. Micro, Lett*. 4(1), 34-39.

Priyaragini, S., Sathishkumar, S. R., Bhaskararao, K. V., 2013. Biosynthesis of silver nanoparticles using actinobacteria and evaluating its antimicrobial and cytotoxicity activity. *Int. J. Pharm. Pharm. Sci*. 5(2), 709-712.

Saminathan, K., 2015. Biosynthesis of silver nanoparticles using soil Actinomycetes *Streptomyces* sp. *Int. J. Curr. Microbiol. App. Sci*. 4(3), 1073-83.

Sastry, M., Ahmad, A., Khan, M. I., Kumar, R., 2003. Biosynthesis of metal nanoparticles using fungi and actinomycete. *Curr. Sci.*, 85(2), 162-170.

Manivasagan, P., Venkatesan, J., Senthilkumar, K., Sivakumar, K., Kim, S. K., 2013. Biosynthesis, antimicrobial and cytotoxic effect of silver nanoparticles using a novel *Nocardiopsis* sp. MBRC-1. *Biomed. Res. Article ID 287638*, pp.1-9.

Vimal, V., Rajan, B. M., Kannabiran, K., 2009. Antimicrobial activity of marine actinomycete, *Nocardiopsis* sp. VITSVK 5 (FJ973467). *Asian. J. Med. Sci*. 1(2), 57-63.

Selvakumar, P., Viveka, S., Prakash, S., Jasminebeaula, S., Uloganathan, R., 2012. Antimicrobial activity of extracellularly synthesized silver nanoparticles from marine derived *Streptomyces rochei*. *Int. J. Pharm. Biol. Sci*, 3(3), 188-197.

Sivakumar, K., Sahu, M. K., Thangaradjou, T., Kannan, L., 2007. Research on marine actinobacteria in India. *Ind. J. Microbiol*. 47(3), 186-196.

Saurav, K., and Kannabiran, K., 2010. Diversity and optimization of process parameters for the growth of *Streptomyces* VITSVK9 spp isolated from Bay of Bengal, India. *Int. J. Environ. Sci*. 1(2), 56-65.

Vijayakumar, R., Murugesan, S., Panneerselvam, A., 2010. Isolation, characterization and antimicrobial activity of actinobacteria from point calimere coastal region, east coast of India. *Int. Res J. Pharam*. 1, 358-365.

Heuer, H., Krsek, M., Baker, P., Smalla, K., & Wellington, E. M., 1997. Analysis of actinomycete communities by specific amplification of genes encoding 16S rRNA and gel-electrophoretic separation in denaturing gradients. *Appl. Environ. Microbiol.* 63(8), 3233-3241.

Naganathan, K., and Thirunavukkarasu, S., 2017. Green way genesis of silver nanoparticles using multiple fruit peels waste and its antimicrobial, anti-oxidant and anti-tumor cell line studies. *Mat. Sci. Eng.* 191(1) pp 012009.

Ganesan, P., Reegan, A. D., David, R. H. A., Gandhi, M. R., Paulraj, M. G., Al-Dhabi, N. A., Ignacimuthu, S., 2017. Antimicrobial activity of some actinomycetes from Western Ghats of Tamil Nadu, India. *Alexandria. Med. J.* 53(2), 101-110.

Abirami, M., and Kannabiran, K. 2016. *Streptomyces ghanaensis* VITHM1 mediated green synthesis of silver nanoparticles: Mechanism and biological applications. *Front. Chem. Sci. Eng.* 10(4), 542-551.

Rathod, D., Golinska, P., Wypij, M., Dahm, H., Rai, M., 2016. A new report of *Nocardiosis valliformis* strain OT1 from alkaline Lonar crater of India and its use in synthesis of silver nanoparticles with special reference to evaluation of antibacterial activity and cytotoxicity. *Med. Microbiol. Immunol.* 205(5), 435-447.

Banerjee, K., and Rai, V. R., 2018. A review on mycosynthesis, mechanism, and characterization of silver and gold nanoparticles. *Bionanosci.* 8(1), 17-31.

Balashanmugam, P., Santhosh, S., Giyaullah, H., Balakumaran, M. D., Kalaichelvan, P. T., 2013. Mycosynthesis, characterization and antibacterial activity of silver nanoparticles from *Microporus xanthopus*: a macro Mushroom. *Int. J. Innov. Res. Sci. Eng. Technol.* 2, 1-9.

Verma, H. N., Singh, P., Chavan, R. M., 2014. Gold nanoparticle: synthesis and characterization. *Vet. World.* 7(2), 72.

Sivalingam, P., Antony, J. J., Siva, D., Achiraman, S., Anbarasu, K., 2012. Mangrove *Streptomyces* sp. BDUKAS10 as nano-factory for fabrication of bactericidal silver nanoparticles. *Colloids. Surf. B Biointerfaces.* 98, 12-17.

Kumar, C. G., and Mamidyala, S. K., 2011. Extracellular synthesis of silver nanoparticles using culture supernatant of *Pseudomonas aeruginosa*. *Colloids. Surf. B Biointerfaces.* 84(2), 462-466.

Krishnaraj, C., Jagan, E. G., Rajasekar, S., Selvakumar, P., Kalaichelvan, P. T., Mohan, N. J. C. S. B. B., 2010. Synthesis of silver nanoparticles using *Acalypha indica* leaf extracts and its antibacterial activity against water borne pathogens. *Colloids. Surf. B Biointerfaces.* 76(1), 50-56.

Shahverdi, A. R., Minaeian, S., Shahverdi, H. R., Jamalifar, H., Nohi, A. A., 2007. Rapid synthesis of silver nanoparticles using culture supernatants of Enterobacteria: a novel biological approach. *Process. Biochem.* 42(5), 919-923.

Kalishwaralal, K., Deepak, V., Ramkumarpandian, S., Nellaiah, H., Sangiliyandi, G., 2008. Extracellular biosynthesis of silver nanoparticles by the culture supernatant of *Bacillus licheniformis*. Mater. Lett. 62(29), 4411-4413.

Manivasagan, P., Venkatesan, J., Senthilkumar, K., Sivakumar, K., Kim, S. K., 2013. Biosynthesis, antimicrobial and cytotoxic effect of silver nanoparticles using a novel *Nocardiopsis* sp. MBRC-1. Biomed. Res. Article ID 287638, pp1-9.A